



Pulsed laser deposition of Cu-Sn-S for thin film solar cells

Ettlinger, Rebecca Bolt; Crovetto, Andrea; Bosco, Edoardo; Rasmussen, P.; Schou, Jørgen

Publication date:
2014

Document Version
Publisher's PDF, also known as Version of record

[Link back to DTU Orbit](#)

Citation (APA):

Ettlinger, R. B., Crovetto, A., Bosco, E., Rasmussen, P., & Schou, J. (2014). Pulsed laser deposition of Cu-Sn-S for thin film solar cells. Poster session presented at World Conference on Photovoltaic Energy Conversion 6, Kyoto, Japan.

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

Pulsed laser deposition of Cu-Sn-S for thin film solar cells

Rebecca Bolt Ettliger¹, Andrea Crovetto², Edoardo Bosco², Philip Rasmussen², Ole Hansen² and Jørgen Schou¹

1. Department of Photonics Engineering, Technical University of Denmark, DK-4000 Roskilde, Denmark

2. Department of Nanotechnology, Technical University of Denmark, DK-2800 Lyngby, Denmark

ABSTRACT

Thin films of copper tin sulfide were deposited from a target of the stoichiometry Cu:Sn:S ~1:2:3 using pulsed laser deposition (PLD). Annealing with S powder resulted in films close to the desired Cu₂SnS₃ stoichiometry although the films remained Sn rich. X-ray diffraction showed that the final films contained both cubic-phase Cu₂SnS₃ and orthorhombic-phase SnS.

1. INTRODUCTION

The ternary chalcogenide Cu₂SnS₃, like the more widely researched material Cu₂ZnSnS₄ (CZTS), can be used as the absorber layer of thin film solar cells [see, e.g. 1, 2]. Pulsed laser deposition is a well-recognized deposition method for compound materials and several groups have used it to deposit CZTS [see, e.g., 3]. We have deposited Cu₂SnS₃ at temperatures below 300 °C, where, however, a number of secondary phases formed. A loss of S and Sn is anticipated with higher deposition or annealing temperature, as needed to obtain good crystal quality [1, 2]. Therefore a Sn and S enriched target was used to deposit precursor films, which were annealed with S powder. The resulting films contain cubic-phase Cu₂SnS₃ with a stoichiometry near the desired Cu:Sn:S ratio of 2:1:3.

2. METHODS

2.1 Pulsed laser deposition

Pulsed laser deposition was done using a 355 nm Nd:YAG laser with 5-7 ns pulses at 10 Hz. The laser beam was rastered across a rotating target in vacuum ($p < 5 \cdot 10^{-6}$ mbar) and the ablated material was deposited on substrates placed 4.5 cm from the target (Fig. 1); the substrates were fused silica or molybdenum-coated soda-lime glass (Mo/SLG). All depositions took place at room temperature. The target was a sintered pellet of copper and tin sulfides (PVD products). The laser spot size was 2.5 mm², the fluence varied from 0.7-2.8 J/cm², and the film thickness varied

from ~1300 nm to ~4200 nm. Annealing was done with S powder in a graphite box held inside a quartz tube with >100 mbar N₂. The temperature was ramped to 500 °C at 12 °C/min, then to 570 °C at 1 °C/min. It remained above 570 °C for 10 min, reaching a maximum of 580 °C, after which the system cooled naturally.

2.2 Characterization

Scanning electron microscopy was performed at 5 keV using the secondary electron detector of a SEM equipped with a field emission gun (FE-SEM, Supra 60VP, Zeiss). Energy dispersive X-ray spectroscopy (EDX) was performed in this SEM using a silicon drift detector (X-Man^N 50, Oxford Instruments) and a beam voltage of 15 kV. On films, full area scans were made at 1000x magnification; on targets, 250x magnification was used. Several measurements were averaged for each sample. The element ratios were calculated using Cu K-lines with Oxford Instruments' Aztec software. When the Mo contribution to the S peak was detectable, the Mo peak was deconvoluted from the spectrum.

X-ray diffraction was done in Bragg-Brentano mode with a Bruker D8 powder diffractometer using a step size of 0.01° and a measurement interval of 1.5 s/step. K_{α2} radiation was subtracted from the data using the program EVA. The diffraction peaks were identified manually and matched to JCPDS files.

3. RESULTS

3.1 Morphology

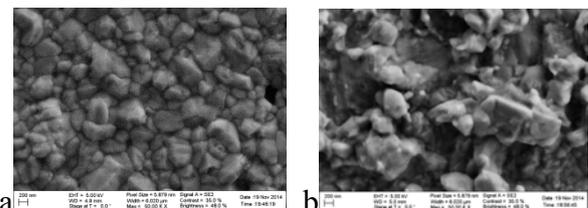


Fig. 1 SEM images of annealed Cu-Sn-S films on Mo/SLG. **a**: deposited at 2.2 J/cm², precursor ~1320 nm thick; **b**: deposited at 0.7 J/cm², precursor ~4200 nm thick. Magnification 50k.

As-deposited films displayed an underlying film dotted with round droplets, similar to CZTS films produced by PLD [4]. The laser fluence had little influence on film appearance.

After annealing, several films contained relatively large grains and visible pinholes (Fig. 1 a) while one thicker film deposited at lower fluence appeared rougher with less well-defined grains (Fig. 1 b). The films with large grains are similar in appearance to Cu_2SnS_3 films annealed in a similar manner by Chino et al. [2].

3.2 Energy dispersive X-ray spectroscopy

The composition of the Sn- and S-enriched target, as-deposited films and annealed films is shown in Fig. 2. Measurements on as-deposited films were made on films on fused silica substrates, whereas annealed films were deposited on Mo/SLG. As-deposited films on Mo/SLG were generally a few absolute percent more Sn and S rich than those on fused silica.

The as-deposited films were Sn- and S-poor compared to the target. The composition did not depend significantly on fluence or laser spot size. Annealing decreased the Sn content while increasing the S content slightly. The stoichiometry of the annealed films is close to Cu_2SnS_3 ; the thickest film is closest. All the films retained an excess of Sn.

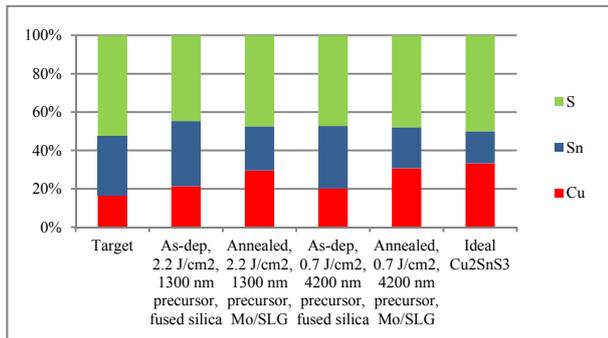


Fig. 2 Composition from EDX of target and selected films.

3.3 X-ray diffraction

As-deposited films on fused silica displayed no obvious X-ray diffraction peaks; films on Mo/SLG were assumed to be similar. After annealing, films form Cu_2SnS_3 (cubic phase) alongside SnS (orthorhombic) (Fig. 3). The thick film shown in Fig. 1 b is dominated by cubic-phase Cu_2SnS_3 , while the thinner films were dominated by SnS (orthorhombic phase).

4. Discussion and conclusion

As seen from the EDX data, S and Sn was lost relative to the target during pulsed laser deposition at room temperature. Annealing further caused loss of Sn, probably in the form of SnS, where the S loss was compensated by the S powder. The pinholes seen in the thinner films (Fig. 1 a) may be evidence of SnS

evaporation [1]. Compared to the thickest film, the pinholes may appear clearly in the thinner films due to more uniform crystallization. The relatively small X-ray diffraction peaks for the thick film may indicate that it is not fully crystallized but contains amorphous regions.

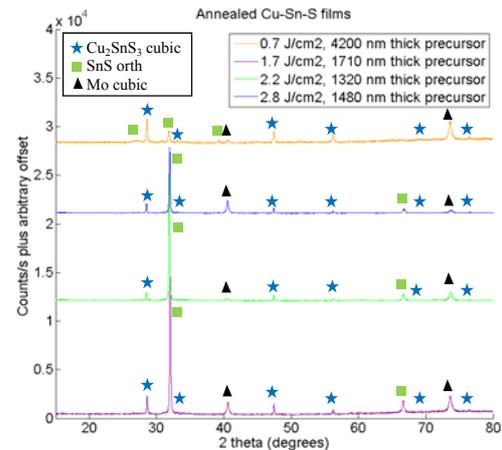


Fig. 3 X-ray diffractograms of films of different thickness made at different fluences. Cubic Cu_2SnS_3 : JCPDS 89-2877; orthorhombic SnS: JCPDS 39-354; cubic Mo: JCPDS 42-1120

In summary, using a Sn- and S-enriched target for pulsed laser deposition of copper tin sulfide, we obtained near-stoichiometric Cu_2SnS_3 thin films after annealing with S above 570 °C. However, the films remain Sn rich and contain SnS. In future work a less enriched target may be used.

REFERENCES

- [1] N. Aihara, H. Araki, A. Takeuchi, K. Jimbo, and H. Katagiri, "Fabrication of Cu_2SnS_3 thin films by sulfurization of evaporated Cu-Sn precursors for solar cells", *Phys. Stat. Sol. C*, **10**, No. 7-8, 1086-1092 (2013).
- [2] K. Chino, J. Koike, S. Eguchi, H. Araki, R. Nakamura, K. Jimbo, H. Katagiri, "Preparation of Cu_2SnS_3 Thin Films by Sulfurization of Cu/Sn Stacked Precursors", *Jpn J Appl Phys* **51**, 10NC35 (2012).
- [3] A. V. Moholkar, S. S. Shinde, G. L. Agawane, S. H. Jo, K. Y. Rajpure, P. S. Patil, C. H. Bhosale, and J. H. Kim, "Studies of compositional dependent CZTS thin film solar cells by pulsed laser deposition technique: An attempt to improve the efficiency", *J. Alloys Compounds*, **544**, 145-151 (2012).
- [4] S. M. Pawar, A. V. Moholkar, I. K. Kim, S. W. Shin, J. H. Moon, J. I. Rhee, and J. H. Kim, "Effect of laser incident energy on the structural, morphological and optical properties of $\text{Cu}_2\text{ZnSnS}_4$ (CZTS) thin films", *Current Appl. Phys.* **10**, 565-569 (2010).