



## Effect of Flow Direction on the Extinction Limit for Flame Spread over Wire Insulation in Microgravity

Nagachi, Masashi ; Mitsui, Fumiya ; Citerne, Jean-Marie ; Dutilleul, Hugo; Guibaud, Augustin ; Jomaas, Grunde; Legros, Guillaume; Hashimoto, Nozomu ; Fujita, Osamu

*Publication date:*  
2017

*Document Version*  
Peer reviewed version

[Link back to DTU Orbit](#)

*Citation (APA):*  
Nagachi, M., Mitsui, F., Citerne, J-M., Dutilleul, H., Guibaud, A., Jomaas, G., ... Fujita, O. (2017). Effect of Flow Direction on the Extinction Limit for Flame Spread over Wire Insulation in Microgravity. Paper presented at 47th International Conference on Environmental Systems, Charleston, United States.

---

### General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

# Effect of Flow Direction on the Extinction Limit for Flame Spread over Wire Insulation in Microgravity

Masashi Nagachi<sup>1</sup>, Fumiya Mitsui<sup>1</sup>, Jean-Marie Citerne<sup>2</sup>, Hugo Dutilleul<sup>2</sup>, Augustin Guibaud<sup>2</sup>  
Grunde Jomaas<sup>3,4</sup>, Guillaume Legros<sup>2</sup>, Nozomu Hashimoto<sup>1</sup>, Osamu Fujita<sup>1</sup>  
<sup>1</sup>*Hokkaido University, Sapporo, Hokkaido, 066-8628, Japan*

<sup>2</sup>*Université Pierre-et-Marie Curie-Paris 6, 78210 Saint-Cyr-l'École, France*

<sup>3</sup>*University of Edinburgh, United Kingdom, EH9 3FG, Edinburgh, United Kingdom*

<sup>4</sup>*Technical University of Denmark, 2800 Kgs. Lyngby, Denmark*

Experiments to determine the Limiting Oxygen Concentration (LOC) of a flame spread over electric wire insulation were carried out in microgravity provided by parabolic flights. The difference between the LOC in opposed and concurrent flows was evidenced. Polyethylene insulated Copper (Cu) wires and polyethylene insulated Nickel-Chrome (NiCr) wires with inner core diameter of 0.50 mm and insulation thickness of 0.30 mm were examined with external flow velocities ranging from 50mm/s to 200mm/s. The results for the Copper wires show that with increasing external flow velocity, the LOC monotonically decreased for the concurrent flow conditions and the LOC first decreased and then increased (“U” trend) for the opposed flow conditions. Similar trends were found in the experiments with NiCr wires. Also, in terms of the minimum LOC value, the minimum LOC was comparable for both wire types in both flow conditions. However, for the concurrent flow, the minimum LOC was about 1-2% lower (in oxygen concentration) than for opposed flow for both wire types. A heat balance model for the electric wire with flame propagation was established to estimate the LOC under opposed and concurrent flow conditions in microgravity. In this model, it was suggested that the LOC can be estimated using the normalized radiative heat loss from the sample surface. Result of the calculation qualitatively matched the LOC profile extracted from the experiments.

## Nomenclature

$c$	=	Specific heat, $J(kgK)^{-1}$
$L_f$	=	Flame length, m
$L_g$	=	Length scale in gas phase, m
$Q_{gs}$	=	Heat conduction from flame to insulation, W
$Q_{rad}$	=	Radiation loss from insulation, W
$Q_{req}$	=	Required energy to heat up insulation until pyrolysis temperature, W
$r$	=	Radius, m
$R_{rad}$	=	Normalized radiative heat loss
$T$	=	Temperature, K
$V$	=	Velocity, m/s
$Y$	=	Mass fraction
$\alpha$	=	Thermal diffusivity, $m^2s^{-1}$
$\varepsilon_s$	=	Emissivity

<sup>1</sup> Division of Mechanical and Space Engineering.

<sup>2</sup> Sorbonne Universités, UPMC Univ Paris 06, UMR 7190, Inst Jean Le Rond d’Alembert, F-75005, Paris, France .

<sup>3</sup> Department of Civil Engineering.

<sup>4</sup> BRE Centre for Fire Safety Engineering

$\eta$	=	Normalized flame spread rate
$\lambda$	=	Thermal conductivity, $W(mK)^{-1}$
$\nu$	=	Stoichiometric ratio
$\rho$	=	Density, $kgm^{-3}$
$\sigma$	=	Stefan-Boltzmann coefficient, $5.67 \times 10^{-8} Wm^{-2}K^{-4}$

**Subscript**

$c$	=	Core wire
$f$	=	Flame
$g$	=	Gas
$O_2$	=	Oxygen
$p$	=	Pyrolysis
$s$	=	Solid (Insulation of wire)
$\infty$	=	Ambient condition

**I. Introduction**

In a spacecraft, ignition of electrical wires can often be the starting point for a fire, and subsequent flame spread over the wire insulation can result in a catastrophic situation. However, work on flame spread over wires in microgravity is very limited despite it having a high potential of causing fires even though much research on flame spread over flat solid samples in microgravity exist.<sup>1,2</sup> Greenberg et al. first conducted experiments on flame spread over wires in a space shuttle. However, details of the mechanisms driving the flame spread over the wires could not be assessed due to the limited number of experiments.<sup>3</sup> Subsequently, the authors of the present work have extensively studied wire insulation combustion in microgravity<sup>4-15</sup> and made an effort to identify the most flammable conditions in microgravity. Takahashi et al. conducted experiments to get the most flammable condition using Nickel-Chrome and copper core wires insulated with polyethylene under opposed air flow conditions.<sup>15</sup> Other related research findings are introduced in the recent review paper by Fujita.<sup>16</sup> While most of the studies investigated opposed flow conditions, Kumar et al. pointed out that the minimum condition of flammability of a flat sheet material in microgravity appeared in concurrent flow condition according to their numerical calculation.<sup>17</sup> Also, authors<sup>18</sup> ran tests of flammability in reduced gravity condition over polyethylene insulated Nickel-chrome wire, and also pointed out that extinction limit of concurrent flow condition was much lower than that of opposed flow condition. However, the reason for such flammability difference between each flow directions is not clarified yet for wire insulation combustion.

The present paper investigates the effect of flow direction, i.e. opposed and concurrent flow, on flammability boundary of a flame spreading over a polyethylene insulated copper wire in reduced gravity ( $\mu g$ ). In this paper, we used the Limiting Oxygen Concentration (LOC) to indicate flammability boundary. It also compares results to data obtained with NiCr core in order to evaluate the influence of core material. Also, a heat balance model of electric wire with flame propagation is introduced to estimate the LOC difference between opposed and concurrent flow conditions in  $\mu g$ .

**II. Experimental apparatus and procedure**

Figure 1 shows the experimental setup for the parabolic flight tests. It consisted of two experimental rigs.

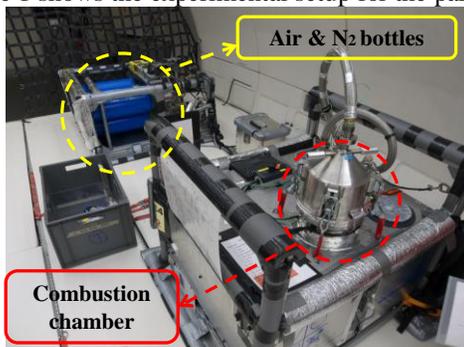


Figure 1. Photo of the experimental setup


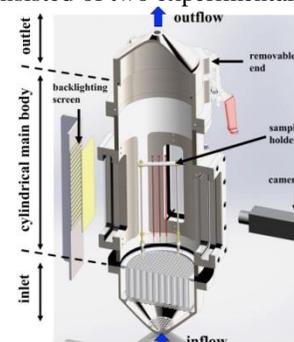


Figure 2. Schematic cut of the experimental setup

The first one was dedicated to the storage of air and nitrogen bottles, which were mixed together using two Bronkhost mass flow controllers to obtain the desired oxidizer concentration and flow velocity. Oxygen concentration in the oxidizer flow could be adjusted from 0 to 21 % and the flow velocity could be set anywhere between 50 and 200 mm/s. The second rig hosted the combustion chamber. Experiments were conducted inside the combustion chamber under  $\mu g$  condition, as shown in Fig. 2. In the combustion chamber, the oxidizer flow entered from the bottom and evacuated at the top. This setup was further described in a paper by Citerne et al<sup>19</sup>. Two cameras were set to capture detailed live information. One camera captured direct flame emission and the other one imaged the flame before a backlighting screen to evaluate the burning rate of molten insulation as well as flame absorption.

The pressure inside the chamber was always set to 1 atmosphere using RCV(Rapid Control Valve) control valve.

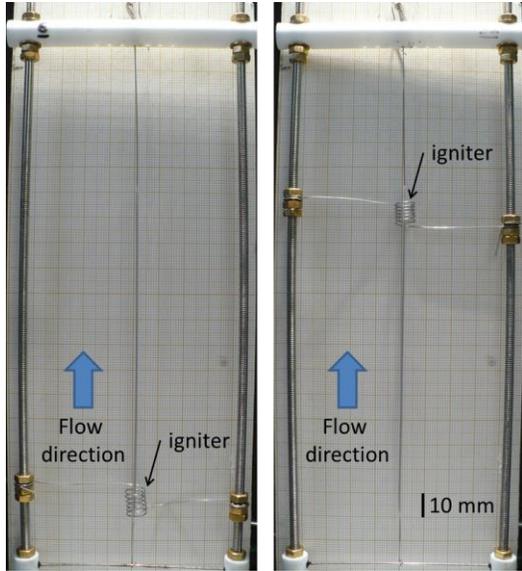

**Figure 3. Picture of samples ready for upward propagation (left) and downward propagation (right) using 6 times wrapped igniter**

The  $\mu g$  condition was obtained from parabolic flights on board of the Novespace A310 airplane. Every parabola enabled  $\mu g$  conditions of about 20 s duration with a g-jitter  $\pm 10^{-2} g_0$ . The parabolic flight had a g-jitter<sup>20,21</sup> of  $10^{-2} g_0$  (0.5~1 Hz), and consequently, a mild flow of around 30 mm/s was expected.<sup>21</sup> Therefore the data obtained with all external flow are expected to have insignificant errors, because all the flow velocities were higher than 30 mm/s. However, when we discuss the trend of LOC vs. external flow velocity such as Fig.4, each plot should have error bar of  $\pm 30$ mm in terms of air flow velocity, which is actually not shown to avoid complication.

### III. Result of the extinction limit


In this study, when a flame is sustained during the whole  $\mu g$  period of each parabola, it is considered as a "propagation" scenario. When the flame is not sustained during the whole period of  $\mu g$ , it is considered an "extinction" scenario. Near the LOC condition, propagation flame was too dim to capture the visible camera. So we judged the propagation and extinction using the movement of molten insulation in the flame using backlighting camera. Then, the LOC is assumed to exist between the maximum extinction case and minimum propagation case. In the past research<sup>18</sup>, there was the comparison between normal gravity and microgravity in terms of LOC using NiCr wire.

Figure 4 and Figure 5 show the extinction limits of spreading flames over NiCr wire and Cu wire in  $\mu g$  under different flow velocity conditions, set by the mass flow controllers. This was single run experiment. One plot shows one experiment. An open circle corresponds to flame propagation conditions in  $\mu g$ , and a cross shows flame extinction conditions in  $\mu g$ . Positive velocities means opposed flow velocity condition, and negative velocities means concurrent flow velocity condition.

**Table 1. Sample wire specification**

Inner core material	Nickel-chrome (NiCr)	Copper (Cu)
Insulation material	Low density polyethylene	
Core diameter [mm]	0.5	
Insulation thickness [mm]	0.3	


Figure 3 shows pictures of the sample holders. Every sample holder had a wire coated with polyethylene over 130 mm. The position of the igniter could vary, in order to enable both opposed and concurrent flow propagation. Table 1 shows the specifications of wire. In this research, two types of core wire: Nickel-chrome (NiCr) and Copper (Cu) wire insulated by Low density polyethylene were used. Core diameter was 0.5 mm, and insulation thickness was 0.3 mm. For the ignition procedure, a 0.5 mm diameter Kanthal wire was wrapped around the leading edge of every insulation coating, and about 94 W were delivered by a power supply along the 8 s long ignition sequence. The shape of igniter was coil, which diameter was as same as M8 screw and winding number was 6 times. We started the ignition sequence before the starting of  $\mu g$ . So ignition occurred in the  $\mu g$ .

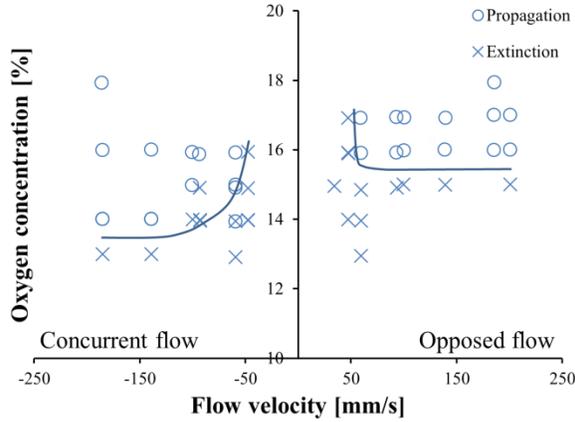

**Figure 4. The LOC of NiCr wire in  $\mu\text{g}$ <sup>18</sup>**

Previous results<sup>18</sup> established using NiCr wires in  $\mu\text{g}$  showed that under opposed flow, the LOC value first decreases with increasing external flow velocity, and then becomes constant. In  $\mu\text{g}$  concurrent flow case, the tendency of LOC is similar to the trend in opposed flow. The minimum LOC for concurrent flow is about 2 % lower in oxygen concentration than that for opposed flow.

With respect to the core wire material, the trend of LOC of Cu wire in both opposed and concurrent flow case are similar to that of NiCr wire, and the minimum LOC of Cu wire is close to that of NiCr wire in both opposed and concurrent flow case. Past results<sup>22</sup> show that the minimum LOC of NiCr wire is lower than that of Cu wire in both opposed and concurrent flow case because the heat loss passed through the core wire is much larger for Cu core wire than for NiCr core wire<sup>22</sup>. However, in this experiment, the difference of the minimum LOC between NiCr wire and Cu wire is quite small. This is because the thickness of the insulation is different. In this experiment, the insulation of the wire is two times thicker compared to the past research one (insulation thickness was 0.15 mm). These fact implies that thicker insulation suppress the effect of thermal conductivity of core material. However, we need more discussion about the effect of core material under different insulation thickness.

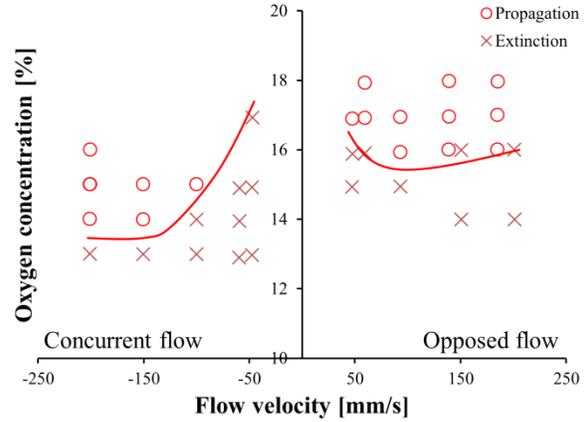


**Figure 5. The LOC of Cu wire in  $\mu\text{g}$**

#### IV. Discussion

According to research by Olson<sup>2</sup>, two types of the extinction phenomena exist, namely quenching extinction in the low flow region, and blow-off extinction in the high flow region. In this research, a physical model is proposed to predict the LOC in low flow region (quenching extinction) of spreading flame over electrical wire. As a base of discussion, the concept of scale analysis carried out by Takahashi et al. is adapted for the case of electrical wire<sup>23</sup>. In this model, NiCr wire was considered to ignore the core wire effect.

##### A. Model of spreading flame over electric wire in opposed flow case

Figure 6 shows the schematics of a flame spread over the wire in opposed flow case. The opposing flow velocity  $V_g$  is due to forced-flow. With respect to the flame, the oxidizer, assumed to be a mixture of oxygen and nitrogen, approaches with a velocity  $V_g$  and the flame spread rate is given as  $V_f$ .

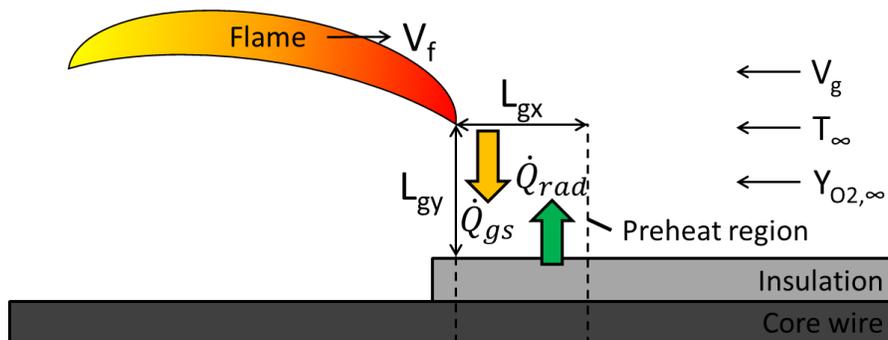

**Figure 6. Schematic of propagating flame in opposed flow (Not to scale)**

This physical model has the assumptions in the following list:

1. Core and insulation are thermally thin for radial direction.
2. Shape of insulation does not change in preheat zone.
3. Heat conduction through core wire is ignored.

In opposed flow case, the length of preheat zone  $L_g$  and height of leading edge of flame were assumed as the following equation.

$$L_g = L_{gx} = L_{gy} = \frac{\alpha_g}{V_g} \quad (1)$$

In the preheat zone, two types of heat transfer were considered; heat conduction from flame to wire ( $Q_{gs}$ ), and radiation loss from wire ( $Q_{rad}$ ). In this model, we assume that there was the minimum flame spread rate to keep the flame propagation. And some energy was needed to keep the minimum flame spread rate from flame. So, an energy balance for the solid phase in preheat zone can be express as follows,

$$Q_{gs} = Q_{rad} + Q_{req} \quad (2)$$

It means that extinction happens when the heat generated by the flame is lost through radiations from insulation and there is not enough energy available to keep the minimum flame spread rate. Using some algebraic manipulations, the equation can be made non-dimensional into the following form:

$$1 = R_{rad.wire} + \eta_{wire} \quad (3)$$

It means that extinction happen when the ratio of radiative energy loss to heat input from flame exceeds critical value. Energies are expressed as follows,

$$\dot{Q}_{gs\_opp} = \frac{2\pi\lambda_g(T_f-T_p)}{\ln(1+\frac{L_g}{r_s})} L_g \quad (4)$$

$$\dot{Q}_{rad\_opp} = 2\pi r_s \epsilon_s \sigma (T_p^4 - T_\infty^4) L_g \quad (5)$$

$$Q_{req\_opp} = V_f \pi \{r_c^2 \rho_c c_c + (r_s^2 - r_c^2) \rho_s c_s\} (T_p - T_\infty) \quad (6)$$

Hence, the energy balance equation from Eq.(2), when substituted into Eq. (4), produce:

$$R_{rad.wire\_opp} = \frac{Q_{rad\_opp}}{Q_{gs\_opp}} = \frac{r_s \epsilon_s \sigma (T_p^4 - T_\infty^4)}{\lambda_g (T_f - T_p) / \ln(1 + L_g / r_s)} \quad (7)$$

$$\eta_{wire\_opp} = \frac{Q_{req\_opp}}{Q_{gs\_opp}} = \frac{V_f \{r_c^2 \rho_c c_c + (r_s^2 - r_c^2) \rho_s c_s\} (T_p - T_\infty)}{2\lambda_g (T_f - T_p) L_g / \ln(1 + L_g / r_s)} \quad (8)$$

To determine the critical value of  $R_{rad.wire\_opp}$ , we give the following equation based on Eq.(3):

$$R_{rad,opp} = 1 - \eta_{wire,opp} = 1 - \frac{Q_{req,opp}}{Q_{gs,opp}} = 1 - \frac{Q_{req,opp}(V_f)}{Q_{rad,opp}(V_g) + Q_{req,opp}(V_f)} \quad (9)$$

From this equation,  $R_{rad,opp}$  can be derived from a steady flame spread rate in a given flow velocity near a extinction limit. In this research, we define that extinction happens in opposed flow case when  $R_{rad.wire\_opp}$  becomes 0.168 from the calculation result of using flame spread rate of  $V_g = 60$  mm/s, which is lowest flow velocity in this experiment. This flame spread rate was experimental data.

## B. Model of spreading flame over electric wire in concurrent flow case

Figure 7 shows the schematics of spreading flame over the wire in concurrent air flow. The concurrent flow velocity  $V_g$  is due to forced-flow. With respect to the flame, the oxidizer, assumed to be a mixture of oxygen and nitrogen, approaches with a velocity  $V_g$  and the flame spreads with a velocity  $V_f$ .

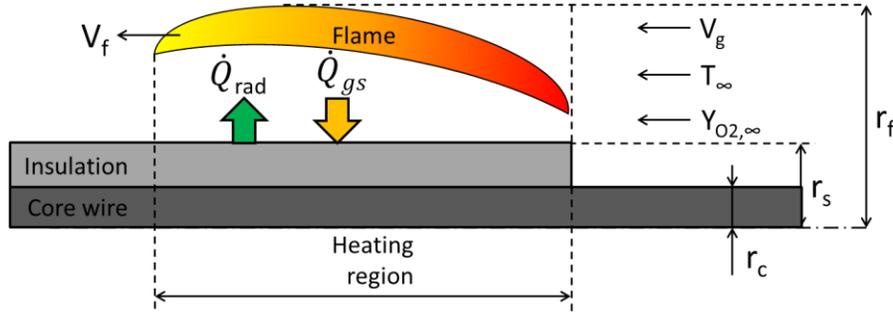


Figure 7. Schematic of propagating flame in concurrent flow (Not to scale)

This physical model has the assumptions in the following list;

1. Core and insulation are thermally thin for radial direction
2. Shape of insulation does not change in preheat zone
3. Steady flame spread is achieved<sup>24</sup>

In this research, the preheat zone in concurrent flow is defined as the flame length,  $L_f$ . Flame height,  $r_f$ , is given by the equation below according to the research by Bhattacharjee et al. based on stoichiometric ratio of fuel and oxidizer<sup>25</sup>.

$$r_f \sim \sqrt{\frac{vV_f \pi (r_s^2 - r_c^2) \rho_s}{\pi V_g \rho_g Y_{O_2, \infty}} + r_s^2} \quad (10)$$

In the same manner as opposed flow case, each of the energies are expressed as follows,

$$\dot{Q}_{gs\_conc} = \frac{2\pi \lambda_g (T_f - T_p)}{\ln(r_f/r_s)} L_f \quad (11)$$

$$\dot{Q}_{rad\_conc} = 2\pi r_s \epsilon_s \sigma (T_p^4 - T_\infty^4) L_f \quad (12)$$

$$\dot{Q}_{req\_conc} = V_f \pi \{r_c^2 \rho_c c_c + (r_s^2 - r_c^2) \rho_s c_s\} (T_p - T_\infty) \quad (13)$$

Hence the energy balance equation leads to:


$$R_{rad\_wire\_opp} = \frac{r_s \epsilon_s \sigma (T_p^4 - T_\infty^4)}{\lambda_g (T_f - T_p) / \ln(r_f/r_s)} \quad (14)$$

$$\eta_{wire} = \frac{V_f \{r_c^2 \rho_c c_c + (r_s^2 - r_c^2) \rho_s c_s\} (T_p - T_\infty)}{2\lambda_g (T_f - T_p) / \ln(r_f/r_s)} \quad (15)$$

In concurrent flow case, the flame heats up the unburned sample widely. It means that the ratio of  $Q_{req}$  to heat input from flame to the sample becomes small because unburned sample is efficiently heated up by combustion gas. So, in this research, we defined that extinction happen in concurrent flow case when  $R_{rad\_wire\_conc}$  is 1.

## C. Estimated trend of LOC based on the proposed model

Figure 8 shows a result of trial to estimate the trend of LOC as a function of opposed and concurrent flow velocity. In this calculation, we assumed the adiabatic flame temperature. So we could change the flame temperature to Oxygen concentration.

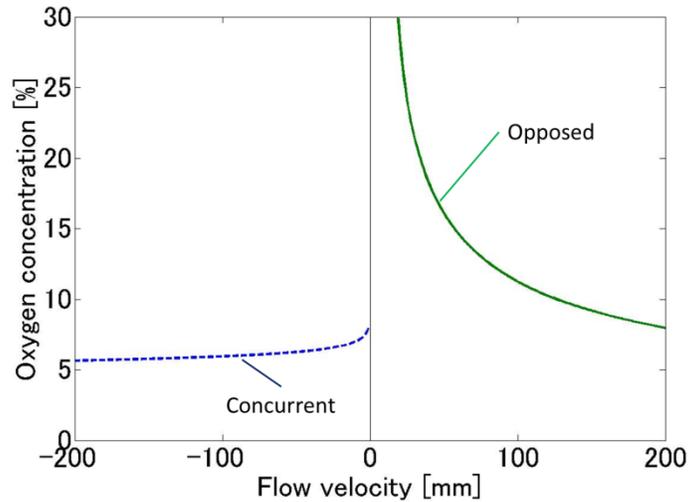

**Figure 8. The calculated result of LOC**

In both case, the LOC decreases with increase in the external flow velocity. Also, in low flow velocity range, the LOC of concurrent flow case is lower than that of opposed flow case. This trend qualitatively matched with the experimental data. If the blow-off extinction curve is superposed to the figure, minimum LOC both in opposed and concurrent could be given at the crossover point of two lines.

However, when the absolute value of the calculation is compared with experimental data, significant discrepancy is found. We need more deep discussion to improve the calculation.

## V. Conclusion

The present work investigated the effect of flow direction on Limiting Oxygen Concentration (LOC) of a spreading flame over Copper (Cu) and Nickel-chrome (NiCr) wire insulation in reduced gravity. The main conclusions of the present study may be summarized as follows:

- (1) According to the flammability tests, LOC in concurrent flow condition was lower than that in opposed flow condition in both NiCr and Cu wire.
- (2) The minimum LOC of NiCr wire was close to that of Cu wire. This is because the insulation of wire was thick, so the effect of the core material was minimized.
- (3) The heat balance model of spreading flame over electrical wire was proposed to explain the LOC difference between opposed flow and concurrent flow conditions using the concept of normalized radiative heat loss value.
- (4) The trend of LOC calculated from the model was qualitatively matched with experimental results.

These results provide insight into the mechanism of extinction limit of flame spread over wire insulation, especially the effect of flow direction on the extinction limit, which will be useful for establishing reliable fire safety standard for spacecraft.

## Appendix

The following the value for the calculation.

- $r_s = 0.00055$ ; radius of wire [m];
- $r_c = 0.00025$ ; radius of core wire [m]
- $\rho_s = 910$ ; density of insulation [kg/m<sup>3</sup>]
- $\rho_c = 8400$ ; density of core material [kg/m<sup>3</sup>]
- $\rho_g = 0.3528$ ; density of gas at 1000K [kg/m<sup>3</sup>]
- $\varepsilon_s = 1$ ; insulation emissivity
- $\sigma = 5.670367E-8$ ; Stefan-Boltzmann coefficient [W/m<sup>2</sup>K<sup>4</sup>]
- $T_p = 710$ ; pyrolysis temperature [K]
- $T_\infty = 300$ ; ambient temperature [K]
- $\lambda_g = 0.06763$ ; thermal conductivity at 1000K [W/mK]

$V_f = 1.3681391E-3$ ; minimum flame spread rate of concurrent flow at 60 mm/s [m/s]  
 $V_f = 7.17E-4$ ; minimum flame spread rate of opposed flow at 60 mm/s [m/s]  
 $c_c = 0.45E3$ ; specific heat of core material [J/kg/K]  
 $c_s = 2.32E3$ ; specific heat of insulation material [J/kg/K]  
 $c_p = 1142$ ; specific heat of gas at 1000K [J/kg/K]  
 $v = 3.4$ ; stoichiometric ratio  
 $\lambda_{O_2} = 0.07046$ ; thermal conductivity of Oxygen at 1000K [W/mK]  
 $c_{p,O_2} = 1089$ ; specific heat of Oxygen at 1000K [J/kg/K]

### Acknowledgments

This research is supported by Japan Space Exploration Agency (JAXA) under the project of FLARE and the Centre National d'Etudes Spatiales (CNES) under contract #130615. The support from the topical team on fire safety in space (ESA-ESTEC contract number 4000103397) is also appreciated. The authors feel grateful to Ulises Rojas Alva for his contributions of the parabolic flight experiment.

### References

- <sup>1</sup>J.S.T'ien, "Diffusion Flame Extinction at Small Stretch Rates: The Mechanism of Radiative Loss," *Combustion and Flame*, Vol. 65, 1986, pp. 31-34.
- <sup>2</sup>S. L. Olson, "Mechanisms of Microgravity Flame Spread Over Solid Fuel: Oxygen and Opposed Flow Effects," *Combust. Sci. and Technol.*, Vol. 76, 1991, pp. 233-249.
- <sup>3</sup>P. S. Greenberg, K. R. Sacksteder, T. Kashiwagi, *Proceedings of the Joint Launch Plus One Year Science Review of USML-1 and USMP-1 with the Microgravity Measurement Group*, NASA CP 3272 2, 1994, pp. 631-655.
- <sup>4</sup>O. Fujita, M. Kikuchi, K. Ito, K. Nishizawa, "Effective mechanisms to determine flame spread rate over ethylene-tetrafluoroethylene wire insulation: Discussion on dilution gas effect based on temperature measurements," *Proc. Combust. Inst.*, 28 (2000) 2905-2911.
- <sup>5</sup>O. Fujita, K. Nishizawa, K. Ito, "Effect of low external flow on flame spread over polyethylene-insulated wire in microgravity," *Proc. Combust. Inst.*, 29 (2002) 2545-2552.
- <sup>6</sup>M. Kikuchi, O. Fujita, K. Ito, J. Sato, T. Sakuraya, "Experimental study on flame spread over wire insulation in microgravity," *Proc. Combust. Inst.* 27 (1998) 2507-2514.
- <sup>7</sup>O. Fujita, T. Kyono, Y. Kido, H. Ito, Y. Nakamura, "Ignition of electrical wire insulation with short-term excess electric current in microgravity," *Proc. Combust. Inst.* 33(2011) 2617-2623.
- <sup>8</sup>Y. Takano, O. Fujita, N. Shigeta, Y. Nakamura, H. Ito, "Ignition limits of short-term overloaded electric wires in microgravity," *Proc. Combust. Inst.* 34(2013) 2665-2673.
- <sup>9</sup>M.K. Kim, S.H. Chung, O. Fujita, "Effect of AC electric fields on flame spread over electrical wire," *Proc. Combust. Inst.* 33 (2011) 1145-1151.
- <sup>10</sup>S. J. Lim, M. K. Kim, J. Park, O. Fujita, S. H. Chung, "Flame spread over electrical wire with AC electric fields: Internal circulation, fuel vapor-jet, spread rate acceleration, and molten insulator dripping," *Combust. Flame* 162 (2015) 1167-1175.
- <sup>11</sup>S. Takahashi, H. Takeuchi, H. Ito, Y. Nakamura, O. Fujita, "Study on unsteady molten insulation volume change during flame spreading over wire insulation in microgravity," *Proc. Combust. Inst.* 34(2013) 2657-2664.
- <sup>12</sup>Y. Nakamura, N. Yoshimura, H. Ito, K. Azumaya, O. Fujita, "Flame spread over electric wire in sub-atmospheric pressure," *Proc. Combust. Inst.* 32 (2009) 2559-2566.
- <sup>13</sup>A. F. Osorio, K. Mizutani, A. C. Fernandez-Pello, O. Fujita, "Microgravity flammability limits of ETFE insulated wires exposed to external radiation," *Proc. Combust. Inst.* 35(3) (2015) 2683-2689.
- <sup>14</sup>L. H. Hu, Y. S. Zhang, K. Yoshioka, H. Izumo, O. Fujita, "Flame spread over electric wire with high thermal conductivity metal core at different inclinations," *Proc. Combust. Inst.*, 35(3) (2015) 2607-2614.
- <sup>15</sup>S. Takahashi, H. Ito, Y. Nakamura, O. Fujita, "Extinction limits of spreading flames over wires in microgravity," *Combust. Flame* 160(9) (2013) 1900-1902.
- <sup>16</sup>O. Fujita, "Solid combustion research in microgravity as a basis of fire safety in space," *Proc. Combust. Inst.* 35(3) (2015) 2487-2502.
- <sup>17</sup>A. Kumar, H. Y. Shih, J. S. T'ien, "A comparison of extinction limits and spreading rates in opposed and concurrent spreading flames over thin solids," *Combustion and Flame*, 132(2003), 667-677
- <sup>18</sup>M. Nagachi, F. Mitsui, K. Kizawa, J.M. Citerne, H. Dutilleul, G. Jomaas, G. Legros, O. Fujita, "Effect of Flow Direction on the Extinction Limit of Spreading Flame over Wire Insulation," *46th International Conference on Environmental Systems ICES-2016-115*
- <sup>19</sup>J. M. Citerne, H. Dutilleul, K. Kizawa, M. Nagachi, O. Fujita, M. Kikuchi, G. Jomaas, S. Rouvreau, J. L. Torero, G. Legros, "Fire Safety in Space – Investigating flame spread interaction over wires", <http://dx.doi.org/10.1016/j.actaastro.2015.12.021>, 2016, *Acta Astronautica*.
- <sup>20</sup>C. Kumar, A. Kumar, "Gravity modulation study on opposed flame spread over thin solid fuels," *Proc. Combust. Inst.* 34

(2013) 2675-2682.

<sup>21</sup>S. Rouvreau, P. Cordeiro, J.L. Torero, "Influence of g-jitter on a laminar boundary layer type diffusion flame", P. Joulain, *Proc. Combust. Inst.* 30 (2005) 519-526.

<sup>22</sup>M. Nagachi, K. Yoshioka, N. Hashimoto, O.Fujita, "Difference of Extinction Limit of Spreading Flame over Polyethylene Insulated Wire between Opposed Air Flow and Concurrent Air Flow", Thermal Engineering Conference 2015

<sup>23</sup>S. Takahashi, M.Horita, S.Bhattacharjee, Y. Ihara, K. Wakai, "Classification of Flame Spread Behavior over a Solid Material by Scale Analysis", *Int. J. Microgravity Sci. Appl.* 10: 9-13 (2012).

<sup>24</sup>X.Zhao, Y.T. Liao, M. Johnston, J.S.T'ien, P.V.Ferkul, S.L.Olson, "Concurrent flame growth, spread, and quenching over composite fabric samples in low speed purely forced flow in microgravity," *Proc. Combust. Inst.* 000 (2016) 1-8.

<sup>25</sup>S. Bhattacharjee, S.Takahashi, K.Wakai, C.P.Paolini, "Correlating flame geometry in opposed-flow flame spread over thin fuels", *Proc. Combust. Inst.* 33 (2011) 2465-2472.