



DFB fiber laser as source for optical communication systems

Varming, Poul; Hübner, Jörg; Kristensen, Martin

Published in:
Optical Fiber Communication. OFC 97., Conference on

Link to article, DOI:
[10.1109/OFC.1997.719791](https://doi.org/10.1109/OFC.1997.719791)

Publication date:
1997

Document Version
Publisher's PDF, also known as Version of record

[Link back to DTU Orbit](#)

Citation (APA):
Varming, P., Hübner, J., & Kristensen, M. (1997). DFB fiber laser as source for optical communication systems. In Optical Fiber Communication. OFC 97., Conference on IEEE. DOI: 10.1109/OFC.1997.719791

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

A highly nonlinear fiber has been fabricated by increasing the nonlinear refractive index by ~ 1.5 times and decreasing the effective area by $\sim 3\times$ over commercial DS fiber. A NOLM formed with this fiber demonstrates improved switching of 1.1 pJ switching in 2 km. For high-speed TDM applications, average control powers are well within current amplifier technology.

*Department of Electrical Engineering and Computer Science, University of Michigan, Ann Arbor, Michigan 48109

**BT Laboratories, Martlesham Heath, Ipswich IP5 7RE U.K.

1. K. Uchiyama, H. Takara, T. Morioka, S. Kawanishi, M. Saruwatari, *Electron. Lett.* **29**, 1313–1314 (1993).
2. K. S. Kim, R. H. Stolen, W. A. Reed, K. W. Quoi, *Opt. Lett.* **19**, 257–259 (1994).
3. D. A. Nolan and W. J. Miller, in *Optical Fiber Communications Conference* Vol. 4 of 1994 OSA Technical Digest Series, (Optical Society of America, Washington, D.C., 1994), pp. 94–95.

WL7

DFB fiber laser as source for optical communication systems


Poul Varming, Jörg Hübner,* Martin Kristensen,* *Department of Electromagnetic Systems, Bldg. 349, Technical University of Denmark, DK-2800 Lyngby, Denmark; E-mail: pv@emi.dtu.dk*

Distributed Bragg reflector (DBR)¹ and distributed feedback (DFB)^{2–4} fiber lasers based on UV-induced Bragg gratings in active fibers are high-quality light sources, which may provide robust single-mode operation without mode hopping. Therefore they constitute an attractive alternative to semiconductor laser sources for optical communication systems. In addition, our DFB fiber lasers offer stable linear polarization with ~ 15 kHz linewidth, excellent signal-to-noise ratio and high-temperature stability.


In the experiment we used 5 cm of $\text{Er}^{3+}:\text{Ge}:\text{Al}$ codoped silica fiber (manufactured by Lycom A/S) spliced to standard fiber pigtailed equipped with angled connectors. The Bragg gratings were photoinduced using a KrF excimer laser illuminating the fiber with 248-nm light through a 5-cm-long phasemask (fabricated by QPS). The induced grating is 4.6 cm long and has a peak reflectivity of 99% at 1555.6 nm. A phase shift was induced in the central part of the grating by additional UV-exposure. The grating was pumped by a semiconductor laser giving 60 mW output around 1475 nm. The lasing was monitored using an optical spectrum analyzer. A scanning Fabry-Perot interferometer was used to verify single-mode operation. Single-mode operation without mode hopping was observed continuously from room temperature up to 200°C and also at -196°C .

The laser has a peak wavelength of 1555.6 nm and a signal-to-noise ratio of 61 dB, measured with a 0.05-nm resolution (left part of Fig. 1). The signal power was 150 μW with 60-mW pumping. When amplifying the laser with a commercially available booster amplifier a signal power of 22 mW was achieved with a signal-to-noise ratio of 44 dB (right part of Fig. 1).

To prove the long-term stability of the laser a transmission experiment at a bit rate of 10 Gbit/s was carried out. The laser was put in a block of aluminum, which was mounted on an optical table. Further temperature stabilization was not necessary as the wavelength drift due to temperature is as low as 0.01 nm/K. The laser was modulated with a $2^{31} -$

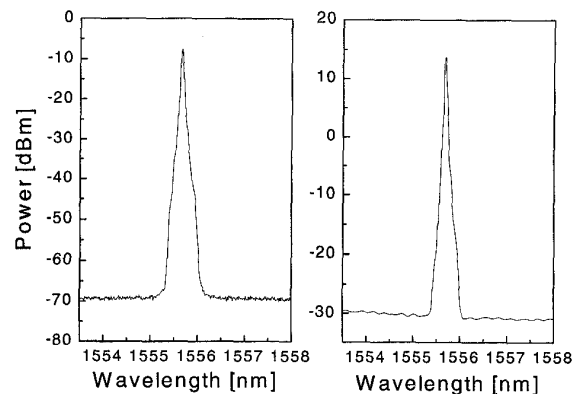

WL7 Fig. 1. Signal-to-noise ratio of DFB fiber laser, measured with a resolution of 0.05 nm. The left figure shows the output directly from the laser and the right figure shows the amplified signal.

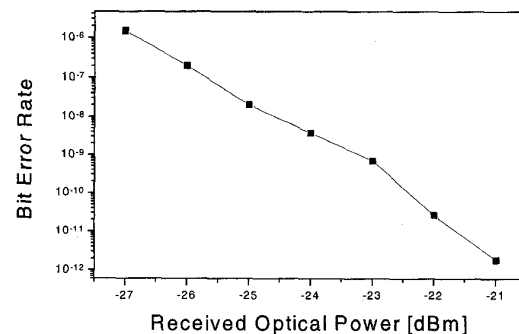

WL7 Fig. 2. 10-Gbit/s BER curve for amplified DFB fiber laser transmitted through 49.5-km standard single-mode fiber.

1 nonreturn to zero (NRZ) pseudorandom bit sequence using a Mach-Zehnder modulator controlled by a 10-Gbit/s transmission error test set. The signal was transmitted over 49.5 km of standard telecommunication fiber with a total loss of 10 dB. The bit-error-rate (BER) curve was measured (Fig. 2) and error-free operation was observed during a measurement time of one hour.

The results demonstrate that DFB fiber lasers are an attractive alternative as sources in telecommunication systems. The lasers show excellent long-term stability with very high signal to noise ratio and a reasonable output power, combined with exceptional temperature stability and inherent fiber compatibility.

*Mikroelektronik Centret, Bldg. 345 e

1. J.L. Zyskind, J.W. Sulhoff, P.D. Magill, K.C. Reichmann, V. Mizrahi, D.J. DiGiovanni, *Electron. Lett.* **29**, 1105–1106 (1993).
2. M. Sejka, P. Varming, J. Hübner, M. Kristensen, *Electron. Lett.* **31**, 1445–1446 (1995).
3. M. Sejka, J. Hübner, P. Varming, M. Nissov, M. Kristensen, in *Optical Fiber Communication Conference*, Vol. 2 of 1996 OSA Technical Digest Series (Optical Society of America, Washington, D.C., 1996), paper TuJ2.
4. J.T. Kringlebotn, J.-L. Archambault, L. Reekie, D.N. Payne, *Opt. Lett.* **19**, 2101–2103 (1994).