



Fiber segmentation from 3D X-ray computed tomography of composites with continuous textured glass fibre yarns

Rasmussen, Filip Salling; Emerson, Monica Jane; Sonne, Mads Rostgaard; Hattel, Jesper Henri; Mikkelsen, Lars Pilgaard; Dahl, Vedrana Andersen

Published in:

Proceedings of 2019 International Conference on Tomography of Materials & Structures

Publication date:

2019

Document Version

Publisher's PDF, also known as Version of record

[Link back to DTU Orbit](#)

Citation (APA):

Rasmussen, F. S., Emerson, M. J., Sonne, M. R., Hattel, J. H., Mikkelsen, L. P., & Dahl, V. A. (2019). Fiber segmentation from 3D X-ray computed tomography of composites with continuous textured glass fibre yarns. In *Proceedings of 2019 International Conference on Tomography of Materials & Structures*

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

FIBER SEGMENTATION FROM 3D X-RAY COMPUTED TOMOGRAPHY OF COMPOSITES WITH CONTINUOUS TEXTURED GLASS FIBER YARNS

Filip S. Rasmussen^{*1}, Monica J. Emerson², Mads R. Sonne¹, Jesper H. Hattel¹, Lars P. Mikkelsen³
and Vedrana A. Dahl²

¹Department of Mechanical Engineering, Technical University of Denmark (DTU), Denmark.

²Department of Applied Mathematics, DTU, Denmark.

³Department of Wind Energy, DTU, Denmark.

Keywords: Micro-tomography, Fiber tracking, Fiber-reinforced polymers, Fiber orientation.

Summary: The current study investigates the applicability of a dictionary-based fiber-detection algorithm for continuous textured glass fiber yarns in fiber-reinforced polymer composites. Additionally, the study discusses options for improving the fiber-detection algorithm so that it is applicable to continuous textured fiber yarns in fiber-reinforced polymers.

1. INTRODUCTION

In recent years, the prospects of advanced X-ray Computed Tomography (XCT) for industrial applications continue to increase. The insights into materials microstructure, delivered by XCT, are of uttermost importance for the production of high-quality composite materials, e.g. Fiber Reinforced Polymers (FRP). Hence, knowledge of the microstructure plays a vital role in optimization within manufacturing of FRPs.

The cross-sectional (2D) spatial distribution of fibers was investigated using Optical Microscopy (OM) in [1,2] and it was shown that a varying fiber distribution has a significant influence on local material behavior during the manufacturing process, i.e. thermo-chemical curing gradients. Destructive methods for 3D microstructure characterization were investigated in [3]. Non-destructive confocal laser scanning microscopy was applied in [4], but this technique is limited to sufficiently transparent samples and limited fields of view. In the study by Emerson et al. [5], unidirectional (UD) glass and carbon FRP composites were characterized using XCT in combination with a segmentation method that is robust to image quality [6]. The method is based on a probabilistic dictionary-based feature-labelling algorithm that does not require manual correction of fiber detections. The precision of the method used in [5] was validated by comparing the obtained fiber diameters and spatial distribution of fibers with similar results from OM and Scanning Electron Microscopy (SEM) in [6]. The current work studies the applicability of the method developed in [5] for fiber tracking of continuous textured fiber yarns in FRPs. Finally, options for extensions of the method will be discussed.

2. EXPERIMENTAL METHOD

The experiments were carried out on a Zeiss Xradia Versa 520 scanner at a voltage of 40kV and a power on 74 μ A using 4x optical magnification. The scan was performed using 4501 projections at binning 2 with a total scan time of 20 hours. The resulting scan has 1000^3 voxels with a voxel size of 1.99 μ m. The fiber-center detection algorithm [5] uses a training step to set up a dictionary of corresponding image and label patches. The dictionary is then used to detect centers of fiber cross-sections in each tomographic slice. In the final tracking step, centers are connected throughout the volume to form 3D fiber trajectories.

3. RESULTS

The fiber-center detections are shown overlaid on 4 different XCT slices in Fig. 1(a). It should be noticed how the fibers with a large orientation angle are often detected as 2 or 3 individual fibers. Fig. 1(b) shows the fiber trajectories, the reader should notice how the additional fiber center detections in fibers with large orientation-

*Corresponding and presenting author: fsras@mek.dtu.dk

angles cause problems for the tracking algorithm (compare red markers in Fig. 1(a) with red trajectories in Fig. 1(b)). A suggestion is to utilize the information about the estimated orientation of the fibers from the fiber tracking algorithm, to improve the precision of the fiber-center detections - this is a subject of ongoing research by the authors.

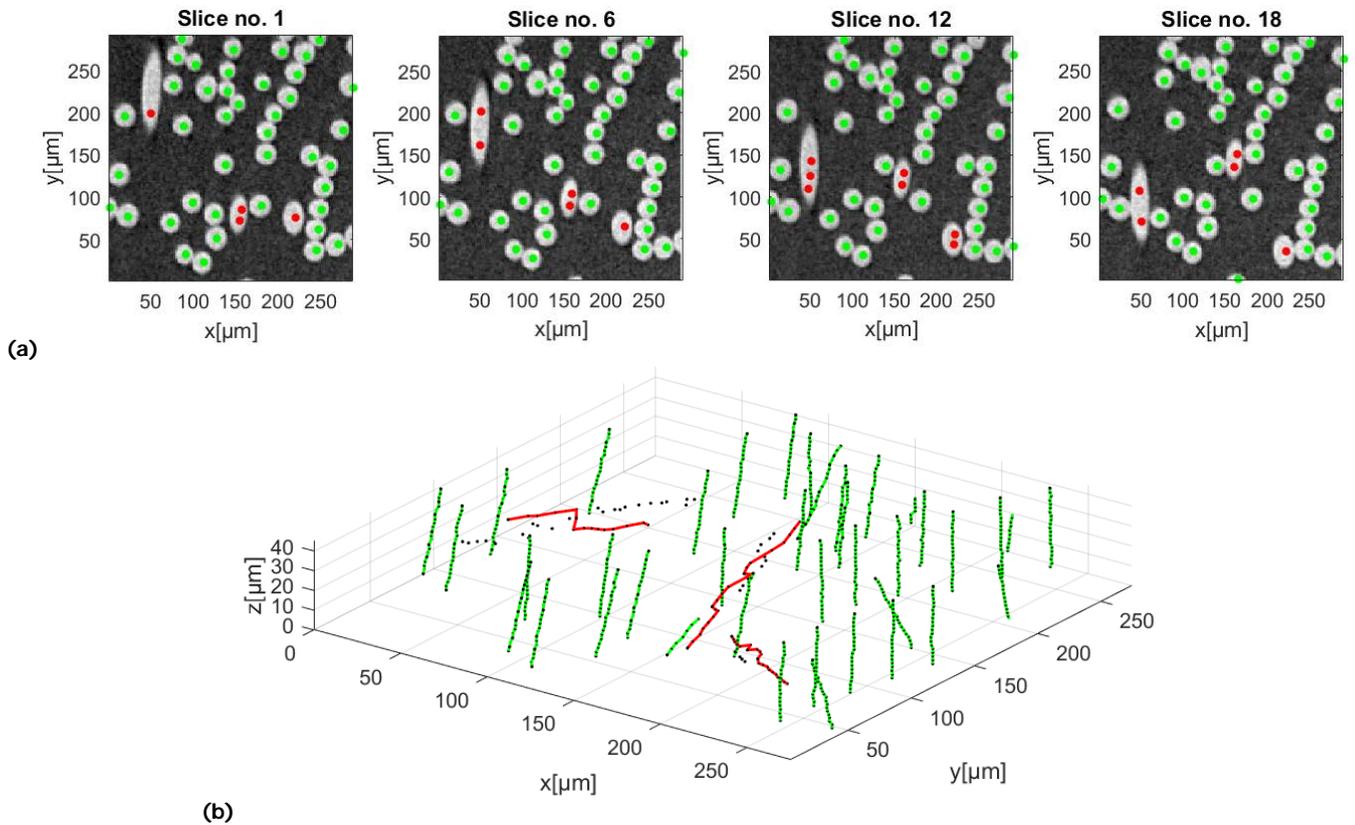


Figure 1: (a) Fiber center detection. (b) Detected centers and the corresponding tracked. The red marker/line color indicates erroneous fiber center detections and tracking.

References

- [1] F.S. Rasmussen, C.G. Klingaa, M. Larsen, M.R. Sonne, J. Spangenberg, and J.H.Hattel. Modelling the Effect of Non-Uniform Fibre Distribution on the Curing Behaviour in Resin Injection Pultrusion, *18th European Conference on Composite Materials, Athens, 2018*.
- [2] O. Yuksel, I. Baran, F.S. Rasmussen, J. Spangenberg, N. Ersoy, J.H. Hattel, and R. Akkerman. Meso-Scale Modelling Strategies for Pultrusion of Unidirectional Profiles. , *18th European Conference on Composite Materials, Athens, 2018*.
- [3] B. Paluch. Analysis of geometric imperfections affecting the fibers in unidirectional composites. *Journal of Composite Materials*, 30:454-485, 1996.
- [4] A.R. Clarke, G. Archenhold, and N.C. Davidson. A Novel Technique for Determining the 3D Spatial Distribution of Glass Fibres in Polymer Composites. *Composites Science and Technology*, 55:75-91, 1995.
- [5] M.J. Emerson, K.M. Jespersen, A.B. Dahl, K. Conradsen & L.P. Mikkelsen. Individual fiber segmentation from 3D X-ray computed tomography for characterizing the fibre orientation in unidirectional composite materials, *Composites Part A: Applied Science and Manufacturing*, 97:83-92, 2017.
- [6] M.J. Emerson, V.A. Dahl, K. Conradsen, L.P. Mikkelsen & A.B. Dahl. Statistical validation of individual fibre segmentation from tomograms and microscopy. *Composites Science and Technology*, 160:208-215, 2018.